



http://www.e-journals.net



ISSN: 0973-4945; CODEN ECJHAO
E-Journal of Chemistry
Vol. 4, No. 4, pp. 487-495, October 2007

Synthesis of Nano-Crystalline $\text{LiNd}_x\text{Mn}_{2-x}\text{O}_4$ Powder by Novel Cam-Microwave Assisted Sol-Gel Method

K. SURYAKALA and R. VENCKATESH*

Lithium ion battery Research Lab, Department of Industrial Chemistry,
Alagappa University, Karaikudi-630 003, Tamilnadu, India

*Advanced Materials Research Laboratory, Department of Science & Humanities,
Kumaraguru College of Technology, Coimbatore - 641 006, Tamilnadu, India.

Received 7 February 2007; Accepted 4 March 2007

Abstract: With the advancement of nanotechnology, there is an interest in the replacement of conventional materials by nanomaterials. There is a reasonable chance that as the active mass of electrode for lithium batteries is comprised of smaller particles, they will perform better in terms of capacity, power, rate capability and stability. LiMn_2O_4 is inexpensive material but it shows rather poor cyclic performance. The electrochemical performance of spinel type LiMn_2O_4 has been effectively improved with doping of Nd the “bottom-up” approach of LiMn_2O_4 and $\text{LiNd}_x\text{Mn}_{2-x}\text{O}_4$ ($x = 0.1, 0.2, 0.3$ and 0.4) synthesized by citric acid modified microwave assisted sol-gel method. LiMn_2O_4 has been synthesized from nitrates and acetates. Citric acid was added as a complexing agent and acryl amide acts as a gelling agent. This technique offers better homogeneity, preferred surface morphology, reduced heat-treatment conditions, sub-micron sized particles and better crystallinity. The structure and the electrochemical performances of the samples are characterized by X-ray diffraction, scanning electron microscopy, transmission electron microscopy, cyclic voltammetry and charge-discharge testing. XRD data shows both samples exhibit the same pure spinel phase. Nano crystalline $\text{LiNd}_{0.3}\text{Mn}_{1.7}\text{O}_4$ sample has a smaller morphology including small particle size and the homogeneous particle distribution compared to the other compositions.

Keywords : Lithium-ion battery; Doped lithium manganese spinels; Cyclic voltammetry;

Introduction

Lithium ion batteries are well regarded as new promising power sources for both portable electronic devices and zero emission vehicles (ZEV) due to their longer cycle life and higher energy density than other rechargeable battery systems. Currently LiCoO_2 ¹, LiNiO_2 ² and LiMn_2O_4 ³ are the main positive electrode materials for lithium-ion batteries. In comparison

LiNiO₂ and LiCoO₂, spinel LiMn₂O₄ has some advantages such as lower cost, higher abundance of Mn in the earth, high safety and lower toxicity⁴. The electrochemical properties of the electrode materials are strongly depends on the physical and chemical properties like crystalline size, stoichiometry, homogeneity etc⁵. However, the preparation of spinel LiMn₂O₄ involves at high temperature as high as 700-900°C solid-state reactions starting from the raw materials, such as manganese oxides, nitrate or carbonate with lithium hydroxide, nitrate or carbonate. The final products usually contains larger irregular particle, in a broader size distribution, as well as impurity phases. And also, this method could not provide good control on the crystalline growth, compositional homogeneity, morphology and microstructure⁶⁻⁹. Therefore, in order to overcome these disadvantages, various new techniques have been developed. Such techniques are based on the processes of co-precipitation, ion-exchange, or thermal decomposition at low temperatures of appropriate organic precursors obtained by sol-gel¹⁰, Pechini¹¹, freeze-drying¹², melt-impregnation¹³, or citric acid gel¹⁴ methods. These methods lead to homogeneous spinel materials with small particle size at the low cost of expensive reagents and process complexity.

In this work, an attempt has been to stabilize the LiMn₂O₄ spinel structure by a Citric Acid Modified (CAM) microwave assisted sol-gel method that employs citric acid as a chelating agent and acryl amide as a gelling agent with cobalt as dopant. This soft chemistry technique offers many advantages such as better homogeneity, low calcination temperature, shorter heating time, regular morphology, sub-micron sized particles, less impurities, large surface area, and good control of stoichiometry.

Experimental

Synthesis procedure

All the chemical reagents used in the experiments were analytical grade without further purification. LiMn₂O₄ and LiNd_xMn_{2-x}O₄ powders were synthesized by citric acid Modified microwave-assisted sol-gel method, which is schematically represented in Figure 1. A stoichiometric amount of lithium nitrate, manganese acetate and neodymium oxide were dissolved in triple distilled water. A calculated amount of citric acid was added as a complexing agent followed by the addition of acryl amide. Here, the acryl amide acts as a gelling agent. The resulting solution was mixed with continuous magnetic stirring at 90 °C until a clear viscous gel occurs. The obtained precursor was preserved under vacuum at 100 °C for 12 h to eliminate water adequately and then was placed in microwave oven. The microwave power operated at 100% (650W) for 20 min. After the microwave treatment, the samples were calcined at 550 °C for 6 h, followed by cooling to room temperature slowly.

Physical characterization

The thermal decomposition behaviour of the LiMn₂O₄ and LiNd_xMn_{2-x}O₄ precursor samples was made using a simultaneous TG/DTA thermal analyzer (STA -1500) at the heating rate of 10 °C/min under ambient atmosphere. The purity and structural conformity of the powder was confirmed by JEOL X-ray diffraction analysis (JDX-8030) using Cu K α radiation. The diffraction patterns were obtained at 25°C in the range 10° \geq 2 θ \leq 70. The step size and scan rate were set at 0.1 and 2 °C min⁻¹, respectively. The shape and size of the microstructure of the particles were observed using Scanning electron microscopy JEOL (JSM-840A) and Transmission electron microscope JEOL – (JEM -100SX).

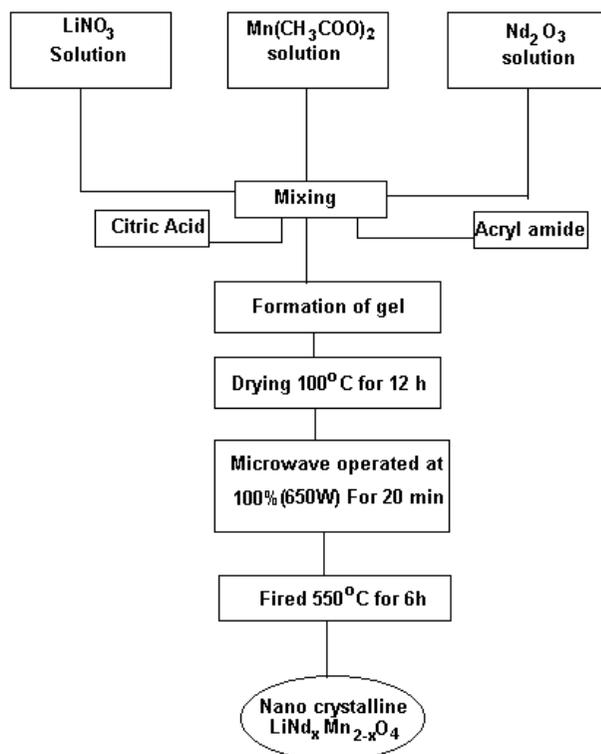


Figure 1. Flow chart for the preparation of cathode materials by CAM microwave assisted sol-gel method.

Electrochemical characterization

In order to assess the cycling behaviour of the synthesized cathode materials, cyclic voltammetry and charge / discharge studies were conducted by fabricating 2016 button-type electrochemical cells with the configuration of $\text{C}/\text{LiMn}_2\text{O}_4$ and $\text{LiNd}_x\text{Mn}_{2-x}\text{O}_4$ and employing Li^+ ion conducting, LiClO_4 electrolyte. The cathode was prepared by mixing synthesized powders, acetylene black and a PVDF (polyvinylidene difluoride) binder dissolved with 2-NMP in a 80: 10:10 weight ratio. The above composite material was mixed and was placed in a die and pressed on to an expanded aluminium foil at a pressure of 5 tones cm^{-2} using a hydraulic press to yield circular pellet electrodes. The pellets were then dried at 110°C in an air oven. Cyclic voltammograms were recorded at a slow scan rate of 1mV/s over the potential range 3-4.5V using an EG&G electrochemical analyzer. The synthesized cathode electrodes were examined for their capacity by constant current charge / discharge at potential window 3.0V – 4.5V at a constant current density of $0.1\text{mA}/\text{cm}^2$ using WonATech Potentiostat/galvanostat instrument (WPG100 South Korea).

Results and Discussion

Thermal analysis

Figure 2 shows the phase formation of LiMn_2O_4 begins at around 305 and 312°C followed by the complete composition of precursor occurred at 425 and 450°C , respectively.

The above discussion revealed that the phase formation and /or complete crystallization of LiMn_2O_4 precursor of citric acid-acryl amide combination occurs at lower temperature.

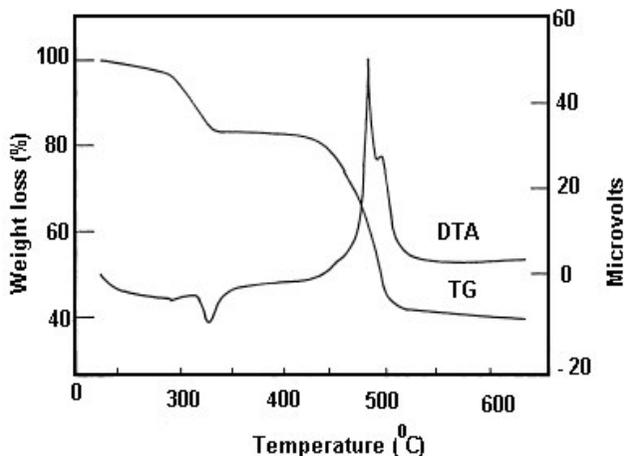


Figure 2. TG/TDA result on $\text{LiNd}_{0.3}\text{Mn}_{1.7}\text{O}_4$

XRD studies

The XRD patterns of products are shown in Figure 3(a-e). The XRD patterns show that the spinel LiMn_2O_4 and $\text{LiNd}_x\text{Mn}_{2-x}\text{O}_4$ powders have pure and crystalline in nature in all the compositions. Impurity phases such as Li_2CO_3 and Mn_2O_3 are often formed in other low temperature synthesis techniques¹⁵ are not observed. The main diffraction peaks of cubic spinel LiMn_2O_4 phase, such as (111), (311) and (400) is well developed. This means that lithium ions occupied tetrahedral 8a sites and manganese also occupied octahedral 16d sites. From the statistics listed in Table 1. It can be seen that $\text{LiNd}_x\text{Mn}_{2-x}\text{O}_4$ has larger lattice parameter (8.2327Å) value comparing with LiMn_2O_4 (8.2077Å).

Table 1. Lattice parameter of samples

Sample	Lattice parameter (Å)	Unit cell volume (Å ³)
LiMn_2O_4	8.2077	552.926
$\text{LiNd}_{0.1}\text{Mn}_{1.9}\text{O}_4$	8.2327	557.984
$\text{LiNd}_{0.2}\text{Mn}_{1.8}\text{O}_4$	8.2325	557.984
$\text{LiNd}_{0.3}\text{Mn}_{1.7}\text{O}_4$	8.2328	557.994
$\text{LiNd}_{0.4}\text{Mn}_{1.6}\text{O}_4$	8.2315	557.990

SEM and TEM analysis

Particle morphology was examined by scanning electron microscopy, which shows that LiMn_2O_4 , $\text{LiNd}_{0.1}\text{Mn}_{1.9}\text{O}_4$, $\text{LiNd}_{0.2}\text{Mn}_{1.8}\text{O}_4$, $\text{LiNd}_{0.3}\text{Mn}_{1.7}\text{O}_4$ and $\text{LiNd}_{0.4}\text{Mn}_{1.6}\text{O}_4$ exhibit homogeneous particle distribution and relatively small particles (micron particle) with similar particle shape. The SEM photographs for undoped and doped $\text{LiNd}_{0.3}\text{Mn}_{1.7}\text{O}_4$ were presented in Figure 4 (a, b). The well dispersed particles are the result of the treatment of microwave as reported elsewhere¹⁶, because the microwave heated from inside of the precursor and thus provided a uniform heating environment which shortened the synthesizing time and overcome the agglomeration of particles¹⁷. Such kind of morphology is very important for both the high specific capacity and good cycleability of the materials¹⁸⁻²⁰.

The SEM studies reveal $\text{LiNd}_{0.3}\text{Mn}_{1.7}\text{O}_4$ material to be of finer size and with less aggregation. It should be most suited cathode material amongst all other compositions.

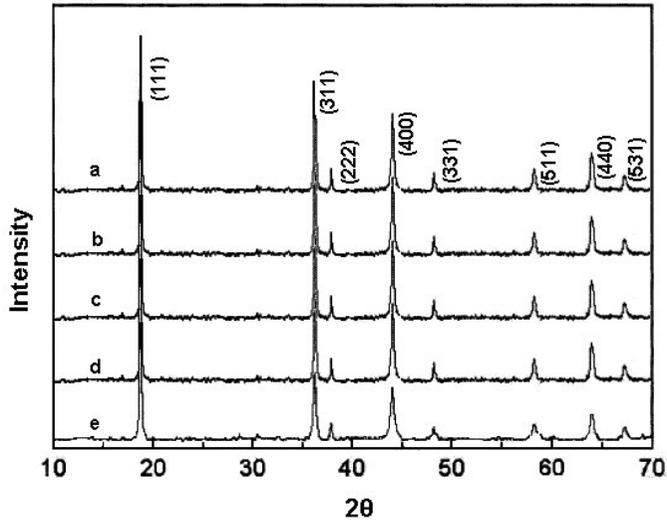


Figure 3. XRD patterns of (a) LiMn_2O_4 (b) $\text{LiNd}_{0.1}\text{Mn}_{1.9}\text{O}_4$ (c) $\text{LiNd}_{0.2}\text{Mn}_{1.8}\text{O}_4$ (d) $\text{LiNd}_{0.3}\text{Mn}_{1.7}\text{O}_4$ and (e) $\text{LiNd}_{0.4}\text{Mn}_{1.6}\text{O}_4$

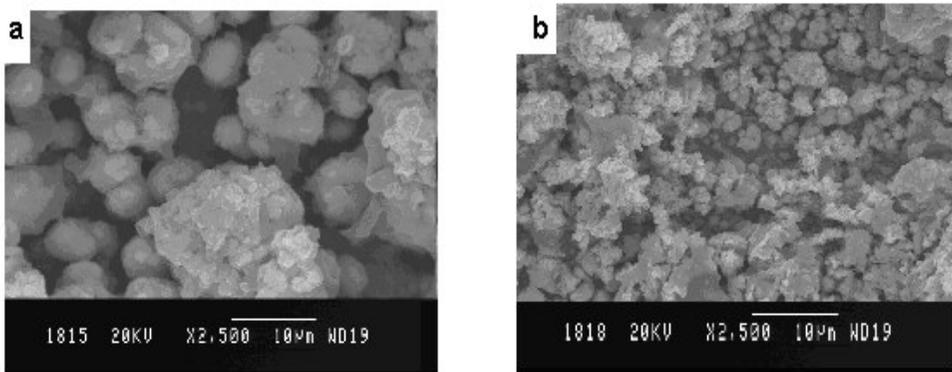


Figure 4. SEM images of (a) LiMn_2O_4 (b) $\text{LiNd}_{0.3}\text{Mn}_{1.7}\text{O}_4$

Hence, TEM study was carried out only for this particular composition to get more clarity on the particle size. The TEM photographs for undoped and $\text{LiNd}_{0.3}\text{Mn}_{1.7}\text{O}_4$ synthesized at 550°C are presented in Figure 5 (a, b). In the case of undoped LiMn_2O_4 the cluster formation is $\approx 60\text{nm}$ and also the particle size is little larger when compared with the Nd doped material $\approx 40\text{nm}$. The interlayer distance may be higher than that of the doped one due to the larger size of particles. The surface area of the electrode material is an important characteristic parameter that determines the energy and power density of a particular battery system. In the present study the surface area is expected to be higher for Nd doped cathode material because of lesser particle size.

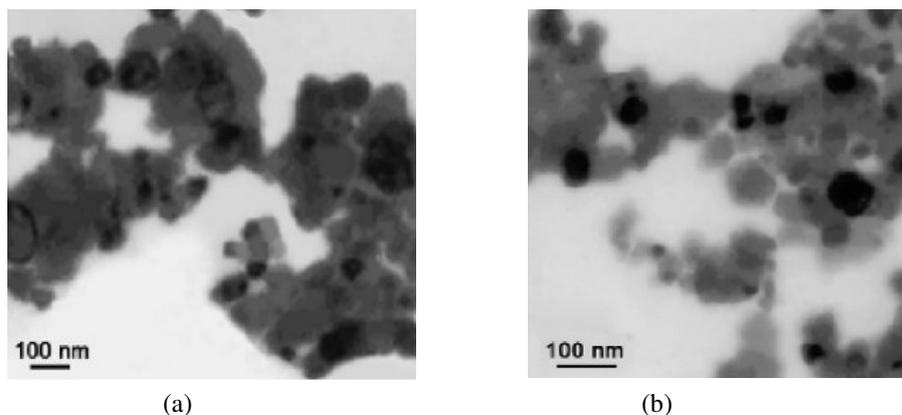


Figure 5. TEM photograph of (a) LiMn_2O_4 (b) $\text{LiNd}_{0.3}\text{Mn}_{1.7}\text{O}_4$

Cyclic voltammetry studies

The electrochemical properties Nd synthesized $\text{LiNd}_x\text{Mn}_{2-x}\text{O}_4$ ($x = 0.0, 0.1, 0.2, 0.3$ and 0.4) were studied through cyclic voltammetric technique. The cathode active materials (80%) were mixed with 10%: 5% weight percentage of acetylene black and polyvinylidene difluoride (PVDF) with N-Methyl-2-pyrrolidone (NMP) binder solution. The prepared paste was casts on pure Al foil and cured at 110°C in a vacuum condition for 24 h. A standard 2016 type coin cell was made using graphite as anode and synthesized material as cathode with polypropylene separator. The electrolyte used 1M LiClO_4 EC (ethylene carbonate) (1:1 v/v). All the setup was done in the argon filled glove box. The cyclic voltammetric properties of the cells were examined between the potential window of 3.0 and 4.5V and the resulting voltammograms are presented in Figure 6(a-e).

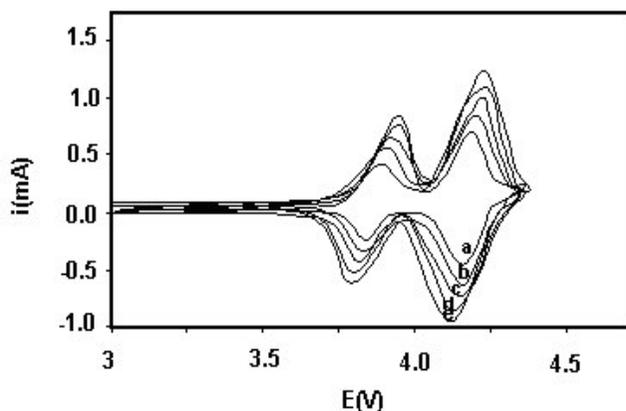


Figure 6. Cyclic voltammetry curve of (a) LiMn_2O_4 (b) $\text{LiNd}_{0.1}\text{Mn}_{1.9}\text{O}_4$ (c) $\text{LiNd}_{0.2}\text{Mn}_{1.8}\text{O}_4$ (d) $\text{LiNd}_{0.3}\text{Mn}_{1.7}\text{O}_4$ and (e) $\text{LiNd}_{0.4}\text{Mn}_{1.6}\text{O}_4$

The intercalation and deintercalation of lithium conveniently takes place in the potential range of interest in all the synthesized materials. Interestingly, the sample prepared $x=0.3$ shows a well-decreased ΔE_p and thus supports the insertion – deinsertion process to be easier.

Charge –discharge studies

The charge –discharge studies were performed at a constant current density of 0.1 mA/cm^2 in the potential range 3.0 – 4.5 V. The recorded voltage capacity curves are shown in Figure 7(a-e) and Figure 8. The first discharge curves show the capacity retention is higher for lower addition while at higher addition the capacity retention is much reduced. In the 50th cycle, the capacity retention is 93.5% for $x = 0.1$; 95.5% for $x = 0.2$; 96.7% for $x = 0.3$; 92.5% for $x = 0.4$ for all the doped cathode materials. However, for undoped material capacity retention is only 90.5%. Alternatively the capacity fading rate of doped and undoped LiMn_2O_4 materials depicted in Figure 9 as bar chart where one could see $\text{LiNd}_{0.3}\text{Mn}_{1.7}\text{O}_4$ cathode material for lithium battery application with capacity fading rate too low when compared to other compositions. The above discussion revealed that the nano-crystalline $\text{LiNd}_{0.3}\text{Mn}_{1.7}\text{O}_4$ has very good reversibility when compared to other compositions. Because the smaller particle size of $\text{LiNd}_{0.3}\text{Mn}_{1.7}\text{O}_4$ facilitates rapid diffusion of Li^+ ions which leads to good battery performance.

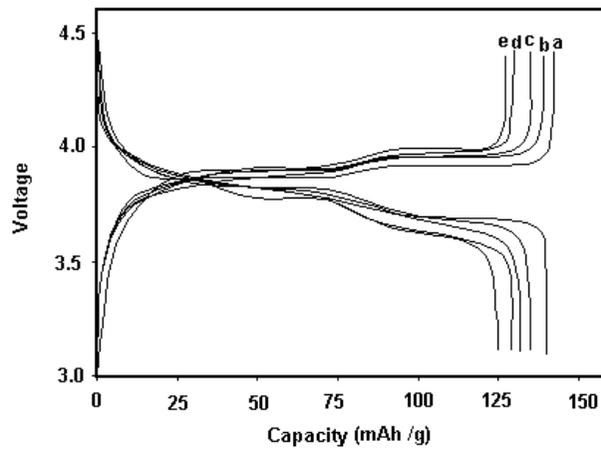


Figure 7. Charge/discharge curve of (a) LiMn_2O_4 (b) $\text{LiNd}_{0.1}\text{Mn}_{1.9}\text{O}_4$ (c) $\text{LiNd}_{0.2}\text{Mn}_{1.8}\text{O}_4$ (d) $\text{LiNd}_{0.3}\text{Mn}_{1.7}\text{O}_4$ and (e) $\text{LiNd}_{0.4}\text{Mn}_{1.6}\text{O}_4$

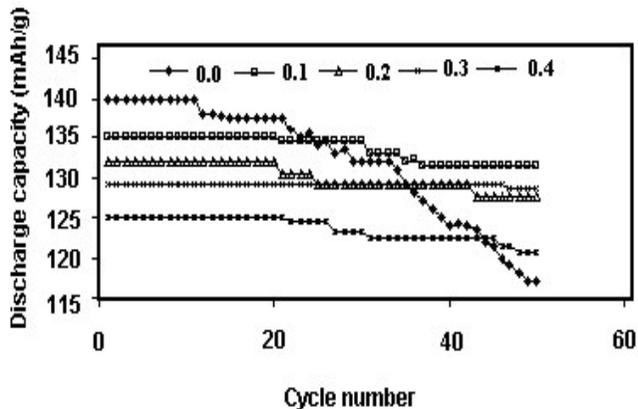


Figure 8. Plots of specific capacity vs. cycle no. of LiMn_2O_4 and $\text{LiNd}_x\text{Mn}_{2-x}\text{O}_4$ ($x = 0.1, 0.2, 0.3$ and 0.4)

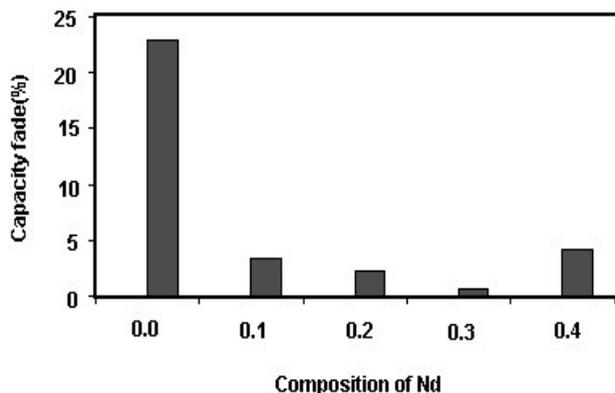


Figure 9. Capacity fading rate vs. in LiMn_2O_4 and $\text{LiNd}_x\text{Mn}_{2-x}\text{O}_4$ ($x = 0.1, 0.2, 0.3$ and 0.4)

Conclusions

Nano-crystalline phase pure LiMn_2O_4 and $\text{LiNd}_x\text{Mn}_{2-x}\text{O}_4$ powders have been synthesized in bulk quantities by CAM microwave assisted sol-gel method. In this study, the rare earth element Nd^{3+} was used as dopant in the LiMn_2O_4 and the structure and the electrochemical properties were examined. XRD data showed that the Nd^{3+} doped sample has the similar phase with undoped sample, but has larger lattice parameter than that of the undoped LiMn_2O_4 . Thermal studies and TEM studies show that $\text{LiNd}_{0.3}\text{Mn}_{1.7}\text{O}_4$ at lower temperature with smaller nanoparticles than other compositions. An electrochemical investigation also shows that the product obtained by $\text{LiNd}_{0.3}\text{Mn}_{1.7}\text{O}_4$ yield better capacity retention than the materials prepared by using other compositions.

Hence, $\text{LiNd}_{0.3}\text{Mn}_{1.7}\text{O}_4$ is the effective composition in CAM microwave assisted sol-gel method for the synthesis of cubic spinel powder and the compound obtained by using this composition is an effective cathode material for lithium ion battery applications.

References

1. Chen Z and Dhan J R, *Electrochim. Acta*, 2004, **49**, 1079.
2. Maruta J and Yamachi H, *J.Power Sources*, 2000, **90**, 89.
3. He X, Li J, Yancaj, Jiang C and Wan C, *Mater.Chem Phys*. 2006, **95**, 105.
4. Wu M, Zhang Q, Lu H and Chen A, *Solid State Ionics*, 2004, **169**, 47-50.
5. Lee Y S, Sun Y K and Nahm K S, *Solid State Ionics*, 1998, **109**, 185.
6. Gan Y and Dahn J R, *J.Electrochem.Soc.* 1996, **143**, 100.
7. Endres P, Fuchs B, Sack S K, Brandt K, Becker G F and Praas H W, *Solid State Ionics*, 1996, **89**, 221.
8. Momchilov A, Manev V, Nassalevska A and Kozawa A, *J.Power Sources*, 1993,**41**, 305.
9. Guan J and Liu M L, *Solid State Ionics*, 1998, **110**, 21.
10. Liu W, Kowal K and Farrington G C, *J.Electrochem.Soc.*, 1996, **143**, 3590
11. Liu W, Farrington G C, Chaput F and Dunn B, *J.Electrochem.Soc.*, 1996, **143**, 879.
12. Zhecheva E N, Gorova M Y and Stoyanova R K, *J.Mater. Chem.*, 1999, **9**, 1559.
13. Xia Y Y, Takeshige H, Noguchi H and Yoshio M, *J.Power Sources*, 1995, **56**, 61.
14. Hwang B J, Santhanam R, Liu D G and Tsai Y W, *J.Power Sources*, 2001, **102**, 326.

15. Hwang B J, Santhanam R and Liu D G, *J. Power Sources*, 2001, **101**, 86.
16. Yang S T, Zhang Y F and Lv Q Z, *J. Inorg. Mater.*, 2000, **15**, 312.
17. Yan H, Huang X and Chen L, *J. Power Sources*, 1999, **81**, 648.
18. Shokoohi F K, Tarascon J M, Wilkers B J, Guyomard D and Chang C C, *J. Electrochem. Soc.* 1992, **139**, 1847.
19. Jang S W, Lee H Y, Shin K C and Lee S M, *J. Power Sources*, 2000, **88**, 274.
20. Myung S T, Chung H T, Komaba S and Kumagai N, *J. Power Sources*, 2000, **90**, 104.



Hindawi

Submit your manuscripts at
<http://www.hindawi.com>

