

## Research Letter

# Surface Adsorption and Replacement of Acid-Oxidized Single-Walled Carbon Nanotubes and Poly(vinyl pyrrolidone) Chains

Wei Chen, Xiaojun Li, and Liming Dai

*Department of Chemical and Materials Engineering, School of Engineering and UDRI, University of Dayton, Dayton, OH 45469-0240, USA*

Correspondence should be addressed to Liming Dai, ldai@udayton.edu

Received 9 June 2007; Accepted 7 September 2007

Recommended by Hans Bettermann

Quartz crystal microbalance (QCM) was used to investigate the adsorption of acid-oxidized single-walled carbon nanotubes (Ox-SWNTs) and poly(vinyl pyrrolidone), PVP. It was found for the first time that Ox-SWNTs adsorbed onto the QCM electrode can be effectively replaced by PVP chains in an aqueous solution. This replacement process was also investigated by atomic force microscopic (AFM) imaging, which shows good agreement with the QCM measurements. This study provides powerful tools for fundamental investigation of polymer-nanotube interactions and for controlled design/fabrication of functional polymer-nanotube surfaces for potential applications.

Copyright © 2007 Wei Chen et al. This is an open access article distributed under the Creative Commons Attribution License, which permits unrestricted use, distribution, and reproduction in any medium, provided the original work is properly cited.

Carbon nanotubes have been demonstrated to possess excellent electronic [1], mechanical [2], and thermal [3] properties attractive for a large variety of potential applications. Examples include their uses as reinforcement fillers in nanocomposite materials and nanoscale building blocks in electronic, photonic, and biomedical devices. With no exception for carbon nanotubes, however, it is very rare that a material with desirable bulk properties also possesses the surface characteristics required for certain specific applications (e.g., strong interface with polymers in nanocomposites, good interfacial properties in colloid systems, and strong biocompatibility for nanotube sensors). Therefore, surface modification becomes essential to render carbon nanotubes dispersible in nanocomposites and to exhibit good bulk and surface properties for biomedical applications. In this context, both chemical and physical approaches have been used for surface modification of carbon nanotubes. Chemical modification of carbon nanotubes with functional molecules [4], including polymer chains [5–9], has been demonstrated to significantly improve their self-assembling properties and compatibility with other material systems. However, these modifications have been shown to alter the nanotube structure, and hence its properties. To conserve the nanotube structure,

physical modification has been used to functionalize carbon nanotube surfaces through the noncovalent adsorption of surfactants [10–13], biomacromolecules [14, 15], or synthetic polymers [16–24]. In particular, it has been demonstrated that many high molecular weight polymers (e.g., poly(vinyl pyrrolidone), PVP; poly-*m*-phenylenevinylene, PmPV) can wrap around the surface of single-walled carbon nanotubes (SWNTs) via hydrophobic-hydrophilic [22–24] and/or  $\pi$ - $\pi$  interactions [25]. Similar to the chemical modification, wrapping carbon nanotubes with appropriate polymer chains could also significantly reduce the intertube van der Waals force thereby enhancing nanotube solubility. Unlike chemical modification, however, the noncovalent (physical) adsorption has advantages in largely retaining the pristine structure and properties of the modified carbon nanotubes.

It is well known that polymer adsorption is a dynamic process, in which adsorbed polymer chains on a particular surface can be desorbed or replaced by other absorbing species that have a greater affinity to the surface [26–29]. The adsorption and desorption processes are important to many fundamental studies and practical applications, including the use of adsorbed polymer chains for stabilization

of colloidal particles, controlled release of drugs, and mimicking cell membranes. As far as we are aware, the possibility for surface replacement between carbon nanotubes and polymers has yet been recognized, though carbon nanotubes, having the large number of well-defined carbon-carbon single and double bonds in their molecular structure, are polymeric in essence. Using quartz crystal microbalance (QCM) and atomic force microscopy (AFM), we found that acid-oxidized single-walled carbon nanotubes (Ox-SWNTs) preadsorbed onto a QCM electrode can be readily replaced by poly(vinyl pyrrolidone), PVP, chains in an aqueous solution. Here, we report our QCM and AFM results from the first study on the surface replacement between carbon nanotubes and polymer chains.

In a typical experiment, 1 mg HiPCo SWNTs (from Tubes@Rice) were oxidized in 8 mL concentrated  $H_2SO_4/HNO_3$  (3/1 w/w) solution under ultrasonication (Branson 2510R, 100 W at 42 KHz) for 1 hour [30, 31], followed by filtration through a Teflon filter of 1- $\mu$ m pores and redispersed in pure (deionized) water to produce an aqueous dispersion of 2 mg/L Ox-SWNTs for subsequent investigation. A platinum-coated AT-cut QCM crystal (9 MHz) of 5 mm in diameter was used as the electrode for the QCM measurements (QCM 922, Princeton Applied Research). Prior to the QCM measurements, the platinum electrode was cleaned electrochemically by scanning 300 cycles between 0 and 1.5 V versus Ag/AgCl electrode in an aqueous solution of 0.5 M  $H_2SO_4$  until a constant frequency was obtained, then repeatedly washed with pure water. The QCM electrode thus cleaned was then transferred into a clean glass cell containing 20 mL pure water, with and without Ox-SWNT and/or PVP, for the frequency/mass measurements. We adopted the well-known Sauerbray equation  $\Delta f = -2\Delta m f^2/A(\mu\rho_q)^{0.5} = -C_f\Delta m$ , using a value of 0.903 Hz/ng for the integrated QCM sensitivity,  $C_f$ , to calculate the “apparent adsorption mass” from the measured frequencies ( $\pm 5$  Hz) [32–35]. QCM results were further verified with AFM imaging. For each of the QCM measurements, AFM imaging (AFM, Digital Instrument NanoScope III) with an SiN tip under tapping mode was performed on a corresponding mica sheet sputter-coated with a thin platinum layer (Denton Vacuum, Desk IV; 40 mA for 5 minutes, *ca.* 20 nm) after having been placed in the same glass cell under the same conditions as for the QCM measurement, followed by rinsing three times with pure water and air dried.

Figure 1(a) shows a time-dependence of the increased mass for adsorption of Ox-SWNTs onto the surface of a QCM platinum electrode. As can be seen, each addition of the 1 mL Ox-SWNT dispersion (2 mg/L) (Figure 1(a)a–d) led to a significant increase in the adsorption mass. The corresponding AFM images given in Figure 2 also show a successive increase in the surface coverage of the adsorbed carbon nanotubes. At the initial adsorption stage (Figures 1(a)a and 2(a)), the platinum surface was only partially covered by the adsorbed Ox-SWNTs. The observed partial surface coverage can be attributed to the low concentration of Ox-SWNTs in the dispersion coupled with a relatively slow adsorption kinetics. Upon the second and third additions of the Ox-SWNT dispersion, much more dramatic increases

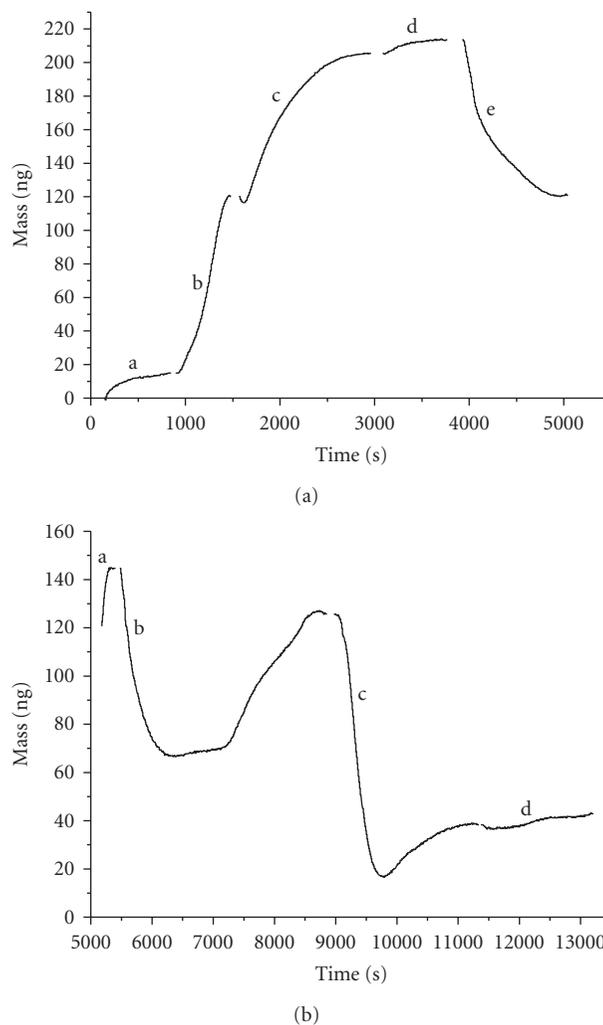


FIGURE 1: Apparent adsorption mass of (a) Ox-SWNT onto a platinum electrode by consecutively adding 1 mL Ox-SWNT dispersion (2 mg/L) four times (a, b, c, and d) into 20 mL water in a glass cell containing the cleaned QCM electrode, followed by thoroughly washing with pure water (e), and (b) the Ox-SWNT preadsorbed QCM platinum electrode (i.e., an electrode corresponding to the end of Figure 1(a)e) after having been thoroughly washed with pure water and reimmersed into 20 mL pure water in the glass cell, to which four 1 mL PVP solution (0.01 g/L) was added consecutively (a, b, c, and d).

in the adsorption mass (Figure 1(a), b and c) and the nanotube surface coverage (Figures 2(b) and 2(c)) were observed for the QCM platinum electrode and the mica-supported platinum surface, respectively. It is worthwhile to note that the adsorbed Ox-SWNTs form some aggregate-like assemblies, leading to somewhat nonuniform distribution of the surface-adsorbed Ox-SWNTs (Figures 2(a)–2(d)). The observed surface-adsorbed nanotube aggregates may arise directly from Ox-SWNT bundles in an aqueous solution with limited dispersion. This scenario is consistent with our observation made on the Ox-SWNT preadsorbed surfaces being subjected to extensive water washing. Figure 1(a)e shows

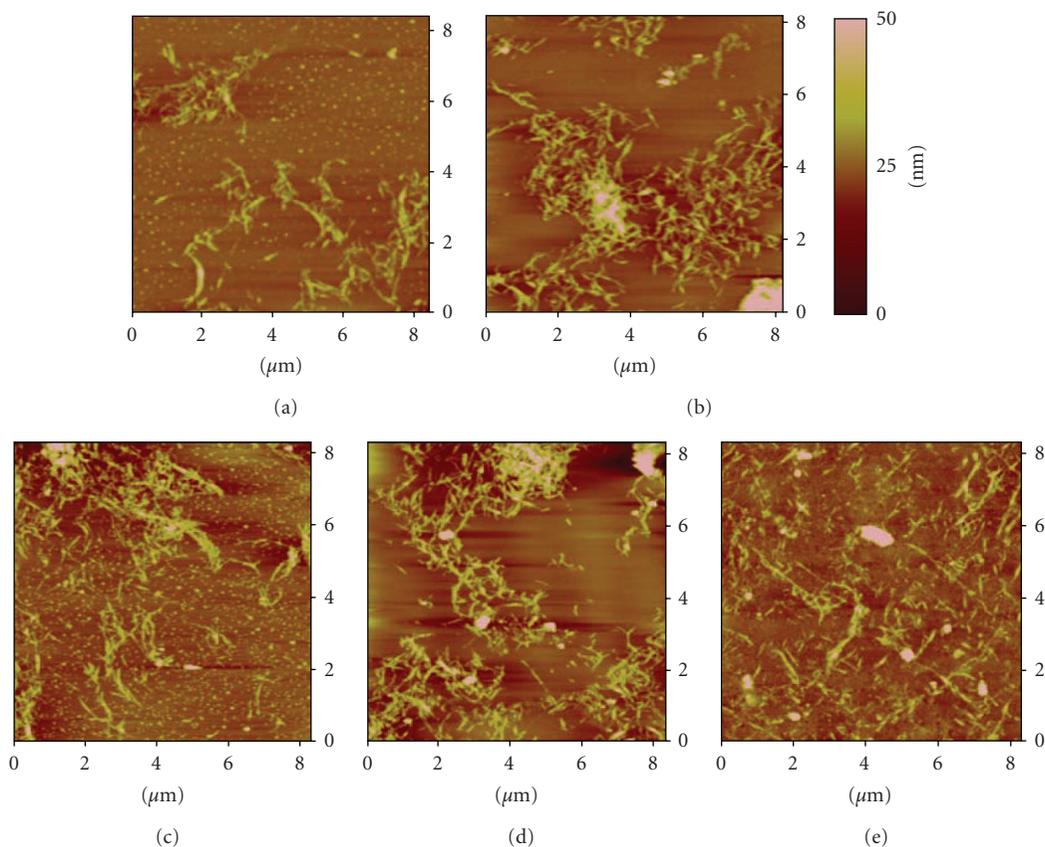


FIGURE 2: Surface coverage of Ox-SWNTs on a platinum sputter-coated mica substrate after consecutively adding 1 mL Ox-SWNT dispersion (2 mg/L) four times (Figures 2(a), 2(b), 2(c), and 2(d)) into 20 mL water in a glass cell containing the cleaned QCM electrode, followed by thoroughly washing with pure water (Figure 2(e)). The scanning ranges for all of the five images are  $8.3 \mu\text{m} \times 8.3 \mu\text{m}$ .

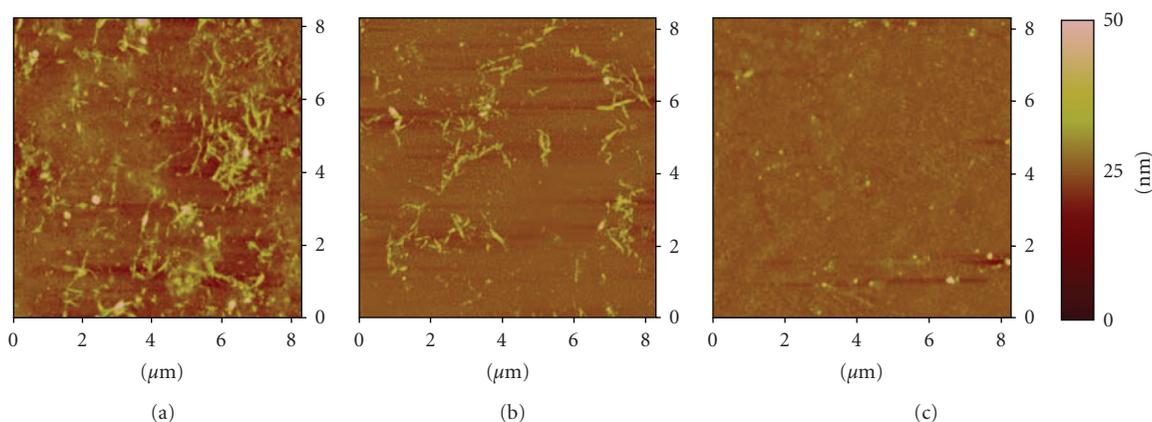


FIGURE 3: Surface coverage of Ox-SWNTs on a platinum sputter-coated mica substrate after consecutively adding 1 mL PVP aqueous solution (0.01 g/L) into 20 mL pure water in the glass cell containing the Ox-SWNT preadsorbed QCM platinum electrode (i.e., an electrode corresponding to the end of Figures 1(a) and 2(e)). Note that the labels of (a), (b), and (c) in the AFM images correspond to the end of the labels of a, b, and c in Figure 1(b), respectively. The scanning ranges for all of the three images are  $8.3 \mu\text{m} \times 8.3 \mu\text{m}$ .

a significant decrease in the absorption mass upon the replacement of the Ox-SWNT dispersion with pure water, followed by thoroughly washing the QCM electrode in the adsorption cell with pure water several times. The observed decrease in the adsorption mass is most probably due to a

washing-induced dissociation of the overlaid Ox-SWNT aggregates into the solution, leading to an equilibrium state for the adsorbed Ox-SWNTs at the liquid/solid interface. The corresponding AFM image given in Figure 2(e) shows some rearrangement of the adsorbed nanotubes to generate a more

homogenous surface coverage for the adsorbed Ox-SWNTs. The overall limiting adsorption mass of Ox-SWNTs was measured to be about 130 ng for the QCM electrode of 5 mm in diameter (Figure 1(a)e). Since each bundle of the Ox-SWNTs is approximately 25 nm in diameter and 1 micron in length with a density of 1.40 g/cm<sup>3</sup> [36], the above measured limiting adsorption mass gives a submonolayer surface coverage of about 10 SWNT bundles per  $\mu\text{m}^2$  corresponding to approximately 25% surface coverage. This surface coverage value of the adsorbed Ox-SWNTs estimated from the QCM measurements corresponds well with the AFM image given in Figure 2(e).

The surface rearrangement seen in Figure 2(e) indicates that there is only a finite affinity of the Ox-SWNTs to the platinum surface, and hence it is possible to replace the preadsorbed Ox-SWNTs by other absorbing species of a high affinity to the surface (e.g., polymers). To investigate the surface replacement between the Ox-SWNTs and polymers, we simply consecutively added a predetermined amount of an aqueous PVP solution (1 mL PVP, 0.01 g/L;  $M_w = 1\,300\,000$ ; Sigma-Aldrich) into 20 mL pure water in the glass cell containing the thoroughly-washed QCM platinum electrode with preadsorbed Ox-SWNTs (i.e., the QCM electrode corresponding to the end of Figure 1(a)e). As can be seen in Figure 1(b), the first addition of the PVP solution caused a slight increase in the adsorption mass, attributable to PVP adsorption into the nanotube-free areas on the QCM platinum electrode and/or onto the preadsorbed nanotube surface. Subsequent additions of the PVP solution led to a tremendous decrease in the adsorption mass due to desorption of the preadsorbed nanotubes, which was followed by an increase in the adsorption mass through additional adsorption of PVP chains into the newly-generated free electrode surface from desorption of nanotubes. The successive desorption of the preadsorbed nanotubes and adsorption of PVP chains could eventually solubilize all the Ox-SWNTs into the solution (*vide infra*).

Further evidence for the replacement of the preadsorbed Ox-SWNTs by PVP chains comes from our AFM images recorded after each addition of the PVP solutions. As can be seen from Figures 3(a)–3(c), the surface coverage of Ox-SWNTs decreased significantly after each of the additions of the PVP solution and incubation for a certain period of time, leading to the disappearance of the majority of the adsorbed nanotubes (Figure 3(c)) and a limited adsorption mass of ca. 40 ng (Figure 1(b)d). Therefore, the value of 40 ng for the limited adsorption mass indicated in Figure 1(b)d must arise predominantly from the adsorbed PVP chains. Given that the PVP molecular weight and the QCM electrode diameter are 1 300 000 and 5 mm, respectively, the above value of the limited adsorption mass (i.e., 40 ng) corresponds to a monolayer coverage of PVP chains [37] on the QCM platinum surface.

Generally speaking, the surface adsorption arises from two opposing interactions; an attractive interaction with the surface favoring adsorption and an attractive interaction with solvent molecules preventing unlimited adsorption. Since adsorption of PVP chains on the Ox-SWNTs could enhance the nanotube solubility in water [22–24], the adsorbed Ox-SWNTs, especially those overlaid on the top of

the nanotube aggregates, can be removed from the surface into the liquid phase by adsorbed polymer chains. This was followed by subsequent absorption of PVP chains onto the newly-generated free surface of platinum.

In summary, we have used the combined quartz microbalance (QCM) and atomic force microscopy (AFM) to demonstrate the first surface replacement of preadsorbed acid-oxidized single-walled carbon nanotubes (Ox-SWNTs) by poly(vinyl pyrrolidone), PVP, chains. We found that carbon nanotubes preadsorbed onto a QCM platinum electrode can be effectively replaced by poly(vinyl pyrrolidone) chains from an aqueous solution. These results would not only open new frontiers for fundamental studies into polymer-nanotube interactions, but also provide powerful tools for the controlled design and fabrication of functional polymer-nanotube surfaces for potential applications, ranging from polymer/nanotube-related micro- or nanoelectronics to biomedical systems.

## ACKNOWLEDGMENTS

The authors thank NSF (NER-0708055), AFRL/ML, Wright Brothers Institute, Dayton Development Collaborations, and University of Dayton for financial support.

## REFERENCES

- [1] P. J. F. Harris, *Carbon Nanotubes and Related Structures: New Materials for the Twenty-First Century*, Cambridge University Press, Cambridge, UK, 1999.
- [2] L. Dai, Ed., *Carbon Nanotechnology: Recent Developments in Chemistry, Physics, Materials Science and Device Applications*, Elsevier, Amsterdam, The Netherlands, 2006.
- [3] M. S. Dresselhaus, G. Dresselhaus, and P. C. Eklund, *Science of Fullerenes and Carbon Nanotubes*, Academic Press, San Diego, Calif, USA, 1996.
- [4] L. Dai, *Intelligent Macromolecules for Smart Devices: From Materials Synthesis to Device Applications*, Springer, Berlin, Germany, 2004.
- [5] S. Qin, D. Qin, W. T. Ford, J. E. Herrera, and D. E. Resasco, "Grafting of poly(4-vinylpyridine) to single-walled carbon nanotubes and assembly of multilayer films," *Macromolecules*, vol. 37, no. 26, pp. 9963–9967, 2004.
- [6] S. Qin, D. Qin, W. T. Ford, et al., "Solubilization and purification of single-wall carbon nanotubes in water by in situ radical polymerization of sodium 4-styrenesulfonate," *Macromolecules*, vol. 37, no. 11, pp. 3965–3967, 2004.
- [7] G. Viswanathan, N. Chakrapani, H. Yang, et al., "Single-step in situ synthesis of polymer-grafted single-wall nanotube composites," *Journal of the American Chemical Society*, vol. 125, no. 31, pp. 9258–9259, 2003.
- [8] S. Qin, D. Qin, W. T. Ford, D. E. Resasco, and J. E. Herrera, "Polymer brushes on single-walled carbon nanotubes by atom transfer radical polymerization of *n*-butyl methacrylate," *Journal of the American Chemical Society*, vol. 126, no. 1, pp. 170–176, 2004.
- [9] H. Kong, C. Gao, and D. Yan, "Constructing amphiphilic polymer brushes on the convex surfaces of multi-walled carbon nanotubes by *in situ* atom transfer radical polymerization," *Journal of Materials Chemistry*, vol. 14, no. 9, pp. 1401–1405, 2004.

- [10] M. J. O'Connell, S. M. Bachilo, C. B. Huffman, et al., "Band gap fluorescence from individual single-walled carbon nanotubes," *Science*, vol. 297, no. 5581, pp. 593–596, 2002.
- [11] C. Richard, F. Balavoine, P. Schultz, T. W. Ebbesen, and C. Mioskowski, "Supramolecular self-assembly of lipid derivatives on carbon nanotubes," *Science*, vol. 300, no. 5620, pp. 775–778, 2003.
- [12] W. Wenseleers, I. I. Vlasov, E. Goovaerts, E. D. Obraztsova, A. S. Lobach, and A. Bouwen, "Efficient isolation and solubilization of pristine single-walled nanotubes in bile salt micelles," *Advanced Functional Materials*, vol. 14, no. 11, pp. 1105–1112, 2004.
- [13] V. C. Moore, M. S. Strano, E. H. Haroz, et al., "Individually suspended single-walled carbon nanotubes in various surfactants," *Nano Letters*, vol. 3, no. 10, pp. 1379–1382, 2003.
- [14] M. Zheng, A. Jagota, M. S. Strano, et al., "Structure-based carbon nanotube sorting by sequence-dependent DNA assembly," *Science*, vol. 302, no. 5650, pp. 1545–1548, 2003.
- [15] M. Zheng, A. Jagota, E. D. Semke, et al., "DNA-assisted dispersion and separation of carbon nanotubes," *Nature Materials*, vol. 2, no. 5, pp. 338–342, 2003.
- [16] P. M. Ajayan, O. Stephan, C. Colliex, and D. Trauth, "Aligned carbon nanotube arrays formed by cutting a polymer resin—nanotube composite," *Science*, vol. 265, no. 5176, pp. 1212–1214, 1994.
- [17] B. McCarthy, J. N. Coleman, R. Czerw, et al., "A microscopic and spectroscopic study of interactions between carbon nanotubes and a conjugated polymer," *The Journal of Physical Chemistry B*, vol. 106, no. 9, pp. 2210–2216, 2002.
- [18] M. in het Panhuis, A. Maiti, A. B. Dalton, et al., "Selective interaction in a polymer-single-wall carbon nanotube composite," *The Journal of Physical Chemistry B*, vol. 107, no. 2, pp. 478–482, 2003.
- [19] J. H. Rouse, "Polymer-assisted dispersion of single-walled carbon nanotubes in alcohols and applicability toward carbon nanotube/sol-gel composite formation," *Langmuir*, vol. 21, no. 3, pp. 1055–1061, 2005.
- [20] A. B. Dalton, C. Stephan, J. N. Coleman, et al., "Selective interaction of a semiconjugated organic polymer with single-wall nanotubes," *The Journal of Physical Chemistry B*, vol. 104, no. 43, pp. 10012–10016, 2000.
- [21] M. in het Panhuis, L. A. P. Kane-Maguire, S. E. Moulton, P. C. Innis, and G. G. Wallace, "Stabilization of single-wall carbon nanotubes in fully sulfonated polyaniline," *Journal of Nanoscience and Nanotechnology*, vol. 4, no. 8, pp. 976–981, 2004.
- [22] M. J. O'Connell, P. Boul, L. M. Ericson, et al., "Reversible water-solubilization of single-walled carbon nanotubes by polymer wrapping," *Chemical Physics Letters*, vol. 342, no. 3–4, pp. 265–271, 2001.
- [23] M. in het Panhuis, C. Salvador-Morales, E. Franklin, et al., "Characterization of an interaction between functionalized carbon nanotubes and an enzyme," *Journal of Nanoscience and Nanotechnology*, vol. 3, no. 3, pp. 209–213, 2003.
- [24] Y. Lin, S. Taylor, H. Li, et al., "Advances toward bioapplications of carbon nanotubes," *Journal of Materials Chemistry*, vol. 14, no. 4, pp. 527–541, 2004.
- [25] R. J. Chen, Y. Zhang, D. Wang, and H. Dai, "Noncovalent sidewall functionalization of single-walled carbon nanotubes for protein immobilization," *Journal of the American Chemical Society*, vol. 123, no. 16, pp. 3838–3839, 2001.
- [26] C. Thies, "The adsorption of polystyrene-poly (methyl methacrylate) mixtures at a solid-liquid interface," *The Journal of Physical Chemistry*, vol. 70, no. 12, pp. 3783–3790, 1966.
- [27] G. J. Fleer, M. A. Cohen Stuart, J. M. H. M. Scheutjens, T. Cosgrove, and B. Vincent, *Polymers at Interfaces*, Chapman & Hall, London, UK, 1993.
- [28] Z. Fu and M. M. Santore, "Kinetics of competitive adsorption of PEO chains with different molecular weights," *Macromolecules*, vol. 31, no. 20, pp. 7014–7022, 1998.
- [29] V. N. Kislenko, "Mathematical model of kinetics of polymer adsorption and replacement adsorption onto a solid surface," *Journal of Colloid and Interface Science*, vol. 202, no. 1, pp. 74–83, 1998.
- [30] B. Kim and W. M. Sigmund, "Functionalized multiwall carbon nanotube/gold nanoparticle composites," *Langmuir*, vol. 20, no. 19, pp. 8239–8242, 2004.
- [31] R. Martel, H. R. Shea, and P. Avouris, "Ring formation in single-wall carbon nanotubes," *The Journal of Physical Chemistry B*, vol. 103, no. 36, pp. 7551–7556, 1999.
- [32] G. Sauerbrey, "Verwendung von Schwingquarzen zur Wägung dünner Schichten und zur Mikrowägung," *Zeitschrift für Physik*, vol. 155, no. 2, pp. 206–222, 1959.
- [33] K. A. Marx, "Quartz crystal microbalance: a useful tool for studying thin polymer films and complex biomolecular systems at the solution—surface interface," *Biomacromolecules*, vol. 4, no. 5, pp. 1099–1120, 2003.
- [34] Y. Yan, X. Zhou, J. Ji, L. Yan, and G. Zhang, "Adsorption of polymeric micelles and vesicles on a surface investigated by quartz crystal microbalance," *The Journal of Physical Chemistry B*, vol. 110, no. 42, pp. 21055–21059, 2006.
- [35] A. Monkawa, T. Ikoma, S. Yunoki, et al., "Fabrication of hydroxyapatite ultra-thin layer on gold surface and its application for quartz crystal microbalance technique," *Biomaterials*, vol. 27, no. 33, pp. 5748–5754, 2006.
- [36] G. Gao, T. Çagin, and W. A. Goddard III, "Energetics, structure, mechanical and vibrational properties of single-walled carbon nanotubes," *Nanotechnology*, vol. 9, no. 3, pp. 184–191, 1998.
- [37] P. C. Painter and M. M. Coleman, *Fundamentals of Polymer Science: An Introductory Text*, CRC Press LLC, Boca Raton, Fla, USA, 2nd edition, 1997.



**Hindawi**

Submit your manuscripts at  
<http://www.hindawi.com>

