

## Research Article

# Second Harmonic of Laser Radiation for IR-Range in Mixed $\text{AgGa}_{0.6}\text{In}_{0.4}\text{Se}_2$ Crystals

Rena J. Kasumova

Physics Department, Baku State University, Z. Khalilov Street 23, AZ1148 Baku, Azerbaijan

Correspondence should be addressed to Rena J. Kasumova; rkasumova@azdata.net

Received 20 November 2013; Accepted 6 January 2014; Published 27 February 2014

Academic Editors: K. Santhakumar and V. Srivastava

Copyright © 2014 Rena J. Kasumova. This is an open access article distributed under the Creative Commons Attribution License, which permits unrestricted use, distribution, and reproduction in any medium, provided the original work is properly cited.

The results of investigations of the influence of different parameters on conversion efficiency in mixed  $\text{AgGa}_{0.6}\text{In}_{0.4}\text{Se}_2$  crystal in conditions of existing experiments are cited. The angular dispersion coefficients for three versions of crystal  $\text{AgGa}_x\text{In}_{1-x}\text{Se}_2$ , differing by a content of indium, have been calculated. A comparison was made of the obtained results on conversion efficiency with analogous results in case of other crystals and with corresponding experimentally measured values. The applied analytical method makes it possible to calculate the optimum parameters of both crystal-converter and a source of radiation for conditions of uncritical phase matching in the concrete experiment.

## 1. Introduction

Recently, the important achievements have been attained in application of nonlinear crystals in the numerous devices of IR-range. One can note among them the prospect  $\text{CdGeAs}_2$  crystals, available  $\text{ZnGeP}_2$  crystals,  $\text{AgGaSe}_2$ , and others [1–3]. Selection of nonlinear crystals is determined by requirement of obtaining the high conversion efficiency of pump radiation in a tuning wide spectral range. As one way of solving this problem, it is suggested to use chalcogenide crystals or chalcopyrite structures, for example,  $\text{AgGa}_x\text{In}_{1-x}\text{Se}_2$ ,  $\text{AgGa}(\text{Se}_{1-x}\text{S}_x)_2$  [2]. In similar crystals, by changing parameter  $x$ , it is possible to realize uncritical  $90^\circ$  phase matching. This condition ensures the absence of walk-off of second harmonic energy, excluding decrease of second harmonic generation caused by birefringence.

We have chosen the perspective crystals  $\text{AgGa}_x\text{In}_{1-x}\text{Se}_2$  as a subject of study among crystals of mixed type, owing to a number of its qualities. As showed in the result of experiment [4] by researchers, by choosing indium content, it is possible to perform the uncritical condition of  $90^\circ$  phase matching at second harmonic generation in near and middle IR-range. With this, a value of parameters  $x$  on wavelength of  $\text{CO}_2$  laser radiation  $\lambda = 9.64 \text{ mcm}$  is equal to 0.6. The measured value of quadratic nonlinear susceptibility for  $\text{AgGa}_{0.6}\text{In}_{0.4}\text{Se}_2$  crystal

is equal to  $d_{36} = 41 \text{ pm/V}$  [4]. For comparison, the analogous specified value for  $\text{AgGaSe}_2$  crystal is equal to  $39 \text{ pm/V}$  [3, 4].

For the task of application in IR-range of spectrum  $\text{CO}_2$  lasers (which present a powerful source of optical coherent radiation in the given region of spectrum) play a leading role. If in the middle IR-region of spectrum an efficient generation of radiation for this laser permits realizing tunable coherent radiation, then in the near IR-range it can succeed owing to radiation of second harmonics for  $\text{CO}_2$  laser.

To consider a wide circle of the tasks in a theory for nonlinear waves, it is necessary to solve the system of coupled nonlinear differential equations. In most cases, solution of such system in a general form is not possible, so to analyze the complete system of reduced equation, different approximation methods have been used. Among them, constant-field approximation of basic radiation was widely used [5–7]. In this approximation, both the real amplitude and phase for wave are considered to be constant. The constant-field approximation depicts rightly only an initial stage of nonlinear interaction for waves until it is not generally possible to take into account the reverse reaction of generated or enforced waves to the intense pump wave. This leads to restricted consideration of wave interaction in real media and loss of information on features of the nonlinear process.

For analyzing of nonlinear process, it is possible to use the direct calculation of coupled equations. However, development of the analytical method will permit receiving the concrete analytical expressions and defining optimum parameters of the task for the purpose of obtaining the maximum efficiency of conversion.

To study the nonlinear optical properties of selected type of crystal, it is expedient to resort to the constant-intensity approximation [8, 9], enabling to take into regard an impact of excited wave on exciting one. The given approximations permitted considering an influence of phase effects on the process of redoubling CO<sub>2</sub> laser radiation frequency in these crystals of mixed type.

In this paper the influence of different parameters of task on conversion efficiency in AgGa<sub>0.6</sub>In<sub>0.4</sub>Se<sub>2</sub> crystal has been investigated in conditions of existing experiments. The angular dispersion coefficients have been calculated for three versions of AgGa<sub>x</sub>In<sub>1-x</sub>Se<sub>2</sub> crystals, differing by content of indium. Comparison of received result on conversion efficiency has been made with analogous result in case of other crystals and with corresponding experimentally measured values. The ways of increasing conversion efficiency are displayed. The used analytical method permits calculating optimum parameters of both crystal-converter and radiation source for conditions of uncritical phase match in the concrete experiment. Thus, for example, we can calculate optimal crystal length at the given losses and the pump intensities, which allows one to estimate expected conversion efficiency.

## 2. Theory

Let us analyze the process of redoubling the frequency of CO<sub>2</sub> laser radiation (at frequency  $\omega_1$ ) in AgGa<sub>x</sub>In<sub>1-x</sub>Se<sub>2</sub> negative uniaxial crystal in case of oo → e scalar phase matching for first type.

For nonlinear conversion, theoretical analysis of wave interaction is made by using the known system of the reduced equation describing second harmonic generation (at frequency 2 $\omega_1$ ) [5-7]:

$$\begin{aligned} \frac{dA_1}{dz} + \delta_1 A_1 &= -i \frac{8\pi^2 d_{1\text{eff}}}{\lambda_1 n(\omega_1)} A_2 A_1^* \exp(-i\Delta z), \\ \frac{dA_2}{dz} + \delta_2 A_2 &= -i \frac{4\pi^2 d_{2\text{eff}}}{\lambda_2 n(\omega_2)} A_1^2 \exp(i\Delta z), \end{aligned} \quad (1)$$

where  $A_1$ ,  $A_2$  are complex amplitudes of pump wave and their second harmonic at frequencies  $\omega_{1,2}$  ( $\omega_2 = 2\omega_1$ ), correspondingly,  $k_1$  and  $k_2$  are values of wave vectors for pump and second harmonic waves,  $\Delta = k_2 - 2k_1$  stands for phase mismatch,  $d_{1,2\text{eff}}$  are efficient nonlinear coefficient for the case oo → e scalar phase matching,  $\lambda_{1,2}$  signify the wavelength of pump and second harmonic waves,  $n(\omega_{1,2})$  are the indices of crystal refraction, and  $\delta_{1,2}$  are the coefficients of absorption for waves at frequencies  $\omega_{1,2}$ , respectively.

System (1) does not include the members that are responsible for thermal effects. In the present work the investigation of frequency conversion for low value of pump intensity is explained.

We will solve the system with the following boundary conditions:

$$A_1(z = 0) = A_{10} \exp(i\varphi_{10}), \quad A_2(z = 0) = 0, \quad (2)$$

where  $z = 0$  corresponds to the entry of crystal and  $\varphi_{10}$  is an initial phase of pump wave at the entry of the medium.

Solution (1) in the constant-intensity approximation which concerns the amplitude of second harmonic while considering the boundary conditions (2) at the output from crystal ( $z = \ell$ ) leads to the following [8, 9]:

$$\begin{aligned} A_2(\ell) &= -i\gamma_2 A_{10}^2 \ell \operatorname{sinc} \lambda\ell \\ &\times \exp \left[ 2i\varphi_{10} - \frac{(\delta_2 + 2\delta_1 - i\Delta_1)\ell}{2} \right], \end{aligned} \quad (3)$$

where

$$\begin{aligned} \lambda^2 &= 2\Gamma^2 - \frac{(\delta_2 - 2\delta_1 + i\Delta_1)^2}{4}, \quad \Gamma^2 = \gamma_1 \gamma_2 I_{10}, \\ \operatorname{sinc} x &= \frac{\sin x}{x}, \quad I_j = A_j A_j^*, \\ \gamma_1 &= \frac{8\pi^2 d_{1\text{eff}}}{\lambda_1 n(\omega_1)}, \quad \gamma_2 = \frac{4\pi^2 d_{2\text{eff}}}{\lambda_2 n(\omega_2)} \end{aligned} \quad (4)$$

are nonlinear coefficients of waves.

From (3) it is seen that the harmonic amplitude depending on length is a periodic function. At first, at the optimal length (coherent length) transferring of basic radiation energy to the second harmonic energy happens. Then a reverse transfer of energy occurs. From (3) at  $\delta_2 = 2\delta_1$  it is possible to receive optimum length of crystal. At this length in the process of frequency conversion, a harmonic signal is maximum  $\ell_{\text{opt}} = \lambda^{-1} \arctan(\lambda/\delta_2)$ , where  $\lambda^2 = 2\Gamma^2 + \Delta^2/4$ . Whence it appears that in this case, in contrast to the results of the constant-field approximation, a coherent length of nonlinear medium depends on pump intensity  $I_{10}$  and dissipation in a medium. By increasing in pump intensity and mismatch, the optimum length decreases. When we ignore the losses  $\ell_{\text{opt}} = 0.5\pi/(2\Gamma^2 + \Delta^2/4)^{1/2}$  [8, 9].

At  $\gamma_1 = 0$  and  $\delta_j = 0$  from (3) we have an expression for conversion efficiency in the constant-field approximation.

From (3) it is possible to obtain the analytical expression for conversion efficiency of pump radiation to second harmonic  $\eta_2(\ell) = I_2(\ell)/I_{10}$ :

$$\eta_2(\ell) = \gamma_2^2 I_{10} \ell^2 \operatorname{sinc}^2 \lambda\ell \exp[-(\delta_2 + 2\delta_1)\ell]. \quad (5)$$

An important requirement for the efficient proceeding nonlinear optical process is the necessity of fulfillment of optimum phase correlation between interacting waves. The violation of this condition leads to mismatch of waves phase and, as a consequence, to decrease of conversion frequency efficiency. One of the basic reasons that cause break of condition of optimum phase correlation is the phase mismatch. At frequency conversion in the conditions of phase mismatch, it is impossible to fulfill the complete transfer of

basic radiation energy to second harmonic energy. In this case the spatial beatings of harmonic amplitudes are observed. This time, the minimums of harmonic intensity beatings, as an analysis shows in the constant-intensity approximation, depend on nonlinear susceptibilities of crystal [10]. This fact permits defining the nonlinear susceptibilities of substances by a simple way, more precise than in the constant-field approximation. With an increase in phase mismatch, spatial frequency increases, but at this time, maximum value of second harmonic intensity decreases.

In the experiment for real frequency converters, it is impossible to ensure a condition of phase agreement, that is, phase matching ( $\Delta = 0$ ). An error in following the condition of phase matching determines the width of phase matching. Spectral width of pump radiation line, deviation from phase matching angle due to divergence of laser radiation, and instability of temperature for a crystal converter all contribute to mismatch. Hence receiving information, in particular, on angular width of phase matching, will permit calculating the maximum divergence of light beam for pumping. Moreover, determination of conditions for realizing uncritical phase matching at chosen length of pump wave is important for exclusion of taking down the influence of birefringent walk-off on generation efficiency. This fact allows one to take away the restriction of length of the used crystals [4, 7, 11].

Let us define an angular width of phase matching in uniaxial crystal for mixed type  $\text{AgGa}_x\text{In}_{1-x}\text{Se}_2$  in case of second harmonic generation of  $\text{CO}_2$  laser radiation on three wavelengths of pump: 9.64 mcm, 9.55 mcm, and 9.31 mcm (scalar phase matching of the first type for  $oo \rightarrow e$  interaction). We will carry out the calculation of deviation angle from the direction of phase matching  $\Delta\theta$  according to [7] for three values reflecting indium content in crystal (0, 0.3, and 0.4). With this, Sellmeier coefficients were used cited in [4, 12].

The results of calculations are presented for angular dispersion coefficient of the first and second orders in Table 1.

### 3. Results and Discussion

To study the ways of increasing frequency conversion efficiency in  $\text{AgGa}_x\text{In}_{1-x}\text{Se}_2$  crystal of  $\text{CO}_2$  laser radiation in IR-range, we will make the numerous calculation of the analytical expression for conversion efficiency (5), received in the constant-intensity approximation; the parameters of the task are chosen according to conditions of existing experiments for the given crystal [4, 13]. In Figures 1–3 the dynamic process of frequency conversion is shown to the second harmonic in  $\text{AgGa}_{0.6}\text{In}_{0.4}\text{Se}_2$  crystal.

In Figure 1, the dependencies of frequency conversion efficiency on length of crystal  $\eta_2(l)$  are presented. These are considered as 3 versions of conversion differing by  $\text{CO}_2$  laser pump intensities, radiating at wavelength in 9.55 mcm. From the behavior of curves differing by monotonous behavior in case of the constant-field approximation, it follows that there exists an optimum value of crystal length at which conversion efficiency is maximum. As far as pump intensity grows the maximum of conversion is reached at lower lengths

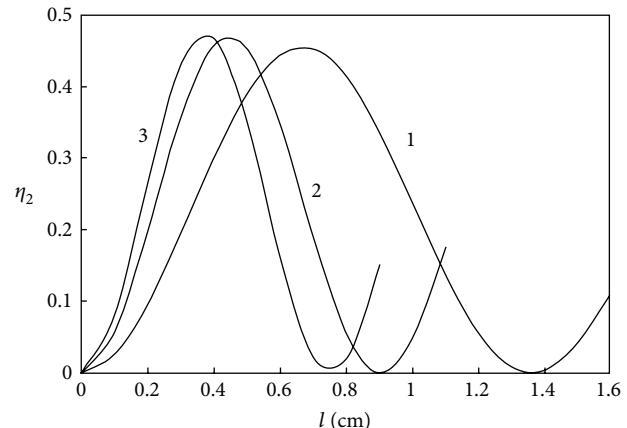


FIGURE 1: Dependences of conversion efficiency of radiation energy of pump wave ( $\lambda = 9.55$  mcm) to energy of wave of second harmonic  $\eta_2$  on lengths of  $\text{AgGa}_{0.6}\text{In}_{0.4}\text{Se}_2$  crystal  $l$  calculated in the constant-intensity approximation for  $\delta_1 = 0.06 \text{ cm}^{-1}$ ,  $\delta_2 = 0.08 \text{ cm}^{-1}$  [4], and  $\Delta = 0.06 \text{ cm}^{-1}$  at pump intensity of  $I_{10} = 0.55 \text{ MW/cm}^2$  (curve 1),  $1.25 \text{ MW/cm}^2$  (curve 2), and  $1.8 \text{ MW/cm}^2$  (curve 3).

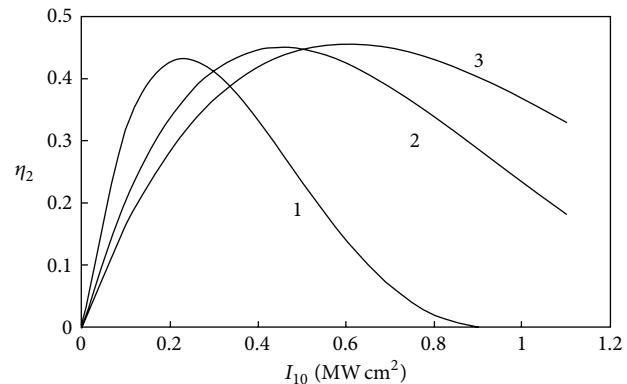


FIGURE 2: Dependences of conversion efficiency of radiation energy of pump wave ( $\lambda = 9.55$  mcm) to energy of second harmonic in  $\text{AgGa}_{0.6}\text{In}_{0.4}\text{Se}_2$  crystal  $\eta_2$  as a function of the pump intensity calculated in the constant-intensity approximation for  $\delta_1 = 0.06 \text{ cm}^{-1}$ ,  $\delta_2 = 0.08 \text{ cm}^{-1}$  [4], and  $\Delta = 0.06 \text{ cm}^{-1}$  at crystal length of  $l = 1.05 \text{ cm}$  [4],  $0.75 \text{ cm}$  (curve 2), and  $0.65 \text{ cm}$  (curve 3).

of a crystal; that is, by increasing the pump intensity, the coherent length of crystal decreases.

In Figure 2, the dependencies on pump intensity for three lengths of crystals are cited. As is seen in the figure,  $\text{CO}_2$  laser radiation, generating at wavelength in 9.55 mcm, maximum efficiency is converted to second harmonic wave at optimum value of pump intensity. From comparison of curves 1, 2, and 3 it is seen that optimum value of pump intensity falls down as crystal length increases. It is explained by the fact that at greater values of pump intensity the coherent length of crystal, where maximum conversion occurs, comes out at lower geometric dimension of crystal-converters.

As is known in the mixed structures  $\text{AgGa}_x\text{In}_{1-x}\text{Se}_2$  crystal properties undergo the influence of indium content [4]. In Figure 3 the results of the analysis for frequency conversion

TABLE 1: The angular dispersion coefficients for  $\text{AgGa}_x\text{In}_{1-x}\text{Se}_2$ .

Crystal	$\lambda$ , mcm	$n_o^\omega$	$n_e^\omega$	$n_o^{2\omega}$	$n_e^{2\omega}$	$d_{36}$ , pm/V	Phase matching type	$\theta_s$ , degree	Angular dispersion coefficient of first order, $\text{cm}^{-1} \cdot \text{ang} \cdot \text{min.}^{-1}$
$\text{AgGaSe}_2$	9.31	2.597798	2.565611	2.616307	2.58463	39.0 [11]	$\text{oo} \rightarrow \text{e}$	47.9 [4] 47.9672	0.048353
$\text{AgGaSe}_2$	9.55	2.596647	2.563607	2.616158	2.584178	39.0 [11]	$\text{oo} \rightarrow \text{e}$	49.1 [4] 49.1893	0.047611
$\text{AgGaSe}_2$	9.64	2.596565 2.596 [4]	2.563902	2.615704 2.583 [2]	2.58401	39.0 [11]	$\text{oo} \rightarrow \text{e}$	49.6 [4] 49.6679	0.046432
$\text{AgGa}_{0.7}\text{In}_{0.3}\text{Se}_2$	9.31	2.606749	2.584379	2.624120	2.602546	40.6 [4]	$\text{oo} \rightarrow \text{e}$	63.5 [4]	0.026456
$\text{AgGa}_{0.7}\text{In}_{0.3}\text{Se}_2$	9.55	2.583259	2.605674	2.623659	2.602059	40.6 [4]	$\text{oo} \rightarrow \text{e}$	65.0 [4]	0.024782
$\text{AgGa}_{0.7}\text{In}_{0.3}\text{Se}_2$	9.64	2.605264	2.582832	2.623489	2.60188	40.6 [4]	$\text{oo} \rightarrow \text{e}$	66.0 [4]	0.023831
$\text{AgGa}_{0.6}\text{In}_{0.4}\text{Se}_2$	9.31	2.609726	2.590959	2.626858	2.608989	41.0 [14]	$\text{oo} \rightarrow \text{e}$	77.6 [4]	0.011648
$\text{AgGa}_{0.6}\text{In}_{0.4}\text{Se}_2$	9.55	2.609726	2.589858	2.626432	2.608496	41.0 [14]	$\text{oo} \rightarrow \text{e}$	83.4 [4]	0.006216
Angular dispersion coefficient of second order, $\text{cm}^{-1} \cdot \text{ang} \cdot \text{min.}^{-2}$									
$\text{AgGa}_{0.6}\text{In}_{0.4}\text{Se}_2$	9.64	2.608277 2.6081 [4]	2.589438	2.626222	2.608315	41.0 [14]	$\text{oo} \rightarrow \text{e}$	90.0 [4]	0.0000194

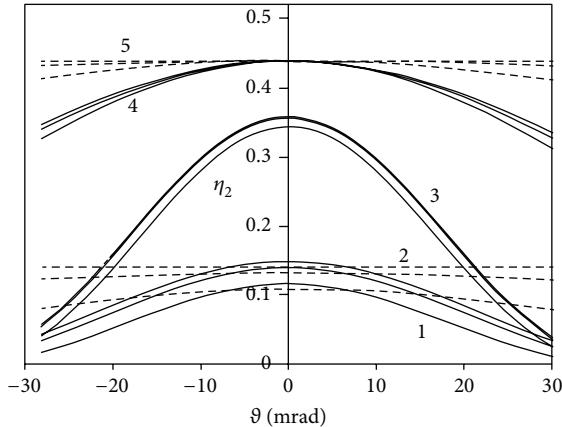


FIGURE 3: Dependences of conversion efficiency of radiation energy of pump wave to energy of wave of second harmonic on  $\text{AgGa}_x\text{In}_{1-x}\text{Se}_2$  crystal  $\eta_2$  as a function of the phase mismatch calculated in the constant-intensity approximation at pump intensity of  $I_{10} = 0.6 \text{ MW/cm}^2$  for  $x = 0.7$ — $\text{AgGa}_{0.7}\text{In}_{0.3}\text{Se}_2$  (groups of curves 1 and 4), 0.6— $\text{AgGa}_{0.6}\text{In}_{0.4}\text{Se}_2$  (groups of dashed curves 2 and 5), and 1— $\text{AgGaSe}_2$  (group of curve 3). In each group, the upper curve corresponds to wavelength of radiation equal to 9.64 mcm, the middle one corresponds to 9.55 mcm, and lower curve corresponds to 9.31 mcm. Here crystal length of  $l = 1.05 \text{ cm}$  [4] (groups of curves 1 and 2), 0.8 cm [4] (group of curve 3), and 0.65 cm (groups of curves 4 and 5). For  $\text{AgGaSe}_2$  crystal  $\delta_1 = 0.09 \text{ cm}^{-1}$ ,  $\delta_2 = 0.15 \text{ cm}^{-1}$  [4] and  $\text{AgGa}_x\text{In}_{1-x}\text{Se}_2$   $\delta_1 = 0.06 \text{ cm}^{-1}$ ,  $\delta_2 = 0.08 \text{ cm}^{-1}$  [4].

process are represented in case of 3 different concentrations of indium in crystal: 0, 0.3, and 0.4. Three versions of CO<sub>2</sub> laser wavelengths are considered: 9.31 mcm, 9.55 mcm, and 9.64 mcm. Groups 1 and 4 (containing three curves each) correspond to dependencies of  $\eta_2(\theta)$  in case of three

wavelengths of pump radiation at lengths of  $\text{AgGa}_{0.7}\text{In}_{0.3}\text{Se}_2$  crystal ( $x = 0.7$ ), equal to 1.05 cm and 0.65 cm, respectively. Groups 2 and 5 (containing on three curves each) correspond to dependencies of  $\eta_2(\theta)$  to three wavelengths of pump radiation at crystal lengths  $\text{AgGa}_{0.6}\text{In}_{0.4}\text{Se}_2$  ( $x = 0.6$ ), equal to 1.05 cm and 0.65 cm. Group 3 (containing three curves) corresponds to dependencies  $\eta_2(\theta)$  in case of 3 wavelengths of pump radiation at length of  $\text{AgGaSe}_2$  crystal ( $x = 1$ ), equal to 0.8 cm. In each group, the upper curve corresponds to wavelength of radiation equal to 9.64 mcm, the middle one corresponds to 9.55 mcm, and lower curve corresponds to 9.31 mcm.

By comparing the behavior of curves 3, 4, and 5, it is seen that with increasing the concentration of indium in the mixed crystal from 1 to 0.6, the dependence  $\eta_2(\theta)$  becomes more flat. It testifies the transition to the regime of uncritical character of crystal towards following condition of phase matching; thus, for instance, in  $\text{AgGaSe}_2$  crystal the change of conversation efficiency by 0.036% takes place in the angular range of changes from  $-0.6 \text{ mrad}$  to  $+0.6 \text{ mrad}$ . Substituting some part of Ga for indium to content  $x = 0.7$  ( $\text{AgGa}_{0.7}\text{In}_{0.3}\text{Se}_2$ ) in a crystal leads to the analogous change of efficiency, but already in the angular range greater by 1.67 times (from  $-1 \text{ mrad}$  to  $+1 \text{ mrad}$ ). The further replacement of indium to crystal to  $x = 0.6$  (i.e.,  $\text{AgGa}_{0.6}\text{In}_{0.4}\text{Se}_2$ ) increases angular range 33 times ( $-20 \text{ mrad}$  to  $+20 \text{ mrad}$ ) in comparison with a case of  $\text{AgGaSe}_2$  crystal. Hence, in  $\text{AgGa}_{0.6}\text{In}_{0.4}\text{Se}_2$  crystal, uncritical behavior towards following phase matching condition is observed in angular range greater than that in  $\text{AgGa}_{0.7}\text{In}_{0.3}\text{Se}_2$  and in  $\text{AgGaSe}_2$ . This question was studied experimentally, in [4], but at the length of experimental sample for  $\text{AgGa}_x\text{In}_{1-x}\text{Se}_2$  crystal equal to 1.05 cm. In our case, it corresponds to curves group 1 ( $x = 0.7$ ) and group 2 ( $x = 0.6$ ). By comparing the curves in groups 1 and 4, and those of groups 2 and 5, we see that the use of optimum length

of a crystal-converter may enable increasing the conversion efficiency three times from  $\eta_2 = 0.15$  to 0.45.

Moreover, it is seen in Figure 3 that in conditions of a real experiment, the maximum expected conversion efficiency in case of  $\text{AgGa}_{0.6}\text{In}_{0.4}\text{Se}_2$  crystal is more than conversion efficiency in  $\text{AgGaSe}_2$  crystal by 1.225 times and only on 0.0378% conversion efficiency in  $\text{AgGa}_{0.6}\text{In}_{0.4}\text{Se}_2$  is more than in  $\text{AgGa}_{0.7}\text{In}_{0.3}\text{Se}_2$  crystal.

Thus, theoretical investigation of frequency conversion in mixed crystals with regard to phase effects enables finding out the ways of increasing conversion efficiency. And, namely, at the given value of crystal converter length it is possible to calculate the optimum value of pump intensity, as well as to calculate the coherent length of crystal-converter at chosen pump intensity of laser radiation. The analytical method also permits estimating an expected conversion efficiency at different wavelengths of lesser radiation. The angular width of phase matching at different concentrations of indium has been estimated for crystals of mixed type. The condition for increasing degree of uncritical angular phase matching is possible to choose.

#### 4. Conclusion


The results of the studies carried out will permit elaborating the reliable highly efficient generators of second harmonic in  $\text{CO}_2$  lasers. The method of analysis for second harmonic generation in  $\text{AgGa}_{0.6}\text{In}_{0.4}\text{Se}_2$  crystals developed in the present work may be used for considering the process of frequency conversion in other perspective crystals of IR-range, as well as for examination of nonlinear optical waves in similar crystals.

#### Conflict of Interests

The author declares that there is no conflict of interests regarding the publication of this paper.

#### References

- [1] S. Das, "Generation of tunable mid-IR radiation by second harmonic in a  $\text{CdGeAs}_2$  crystal," *Quantum Electronics*, vol. 42, no. 3, pp. 228–230, 2012.
- [2] P. P. Geiko, "Phase matching and group-velocity matching conditions in nonlinear mixed  $\text{AgGa}(\text{Se}_{1-x}\text{S}_x)$  crystals," *Atmospheric and Oceanic Optics*, vol. 16, pp. 828–834, 2003.
- [3] P. G. Schunemann, S. D. Setzler, and T. M. Pollak, "Phase-matched crystal growth of  $\text{AgGaSe}_2$  and  $\text{AgGa}_{1-x}\text{In}_x\text{Se}_2$ ," *Journal of Crystal Growth*, vol. 211, no. 1–4, pp. 257–264, 2000.
- [4] Y. M. Andreev, S. I. Baturin, P. P. Geiko, and A. I. Gusamov, " $\text{CO}_2$  laser frequency doubling in a new nonlinear  $\text{AgGa}_{1-x}\text{In}_x\text{Se}_2$  crystal," *Quantum Electronics*, vol. 29, no. 10, pp. 904–908, 1999.
- [5] N. Blombergen, *Nonlinear Optics*, W. A. Benjamin, New York, NY, USA, 1965.
- [6] S. A. Akhmanov and R. V. Khokhlov, *Problemy Nelineynoy Optiki [The Problems of Nonlinear Optics]*, VINITI, Moscow, Russia, 1964.
- [7] V. G. Dmitriev and L. V. Tarasov, *Prikladnaya Nelineynaya Optika [Applied Nonlinear Optics]*, Radio I Svyaz, Moscow, Russia, 1982.
- [8] Z. H. Tagiev and A. S. Chirkin, "Fixed intensity approximation in the theory of nonlinear waves," *Zhurnal Eksperimentalnoi i Teoreticheskoi Fiziki*, vol. 73, pp. 1271–1282, 1977.
- [9] Z. H. Tagiev, R. J. Kasumova, R. A. Salmanova, and N. V. Kerimova, "Constant-intensity approximation in a nonlinear wave theory," *Journal of Optics B*, vol. 3, no. 3, pp. 84–87, 2001.
- [10] Z. A. Tagiev and R. J. Kasumova, "Determination of nonlinear high-order susceptibilities," *Optics and Spectroscopy*, vol. 80, no. 6, pp. 848–850, 1996.
- [11] Y. M. Andreev, P. P. Geiko, A. I. Gusamov, L. G. Geyko, and V. G. Voevodin, "Optical properties of  $\text{AgGa}_x\text{In}_{1-x}\text{Se}_2$  crystals," *Japanese Journal of Applied Physics*, vol. 39, pp. 94–95, 2001.
- [12] G. C. Bhar, S. Das, U. Chatterjee, and K. L. Vodopyanov, "Temperature-tunable second-harmonic generation in zinc germanium diphosphide," *Applied Physics Letters*, vol. 54, no. 4, pp. 313–314, 1989.
- [13] P. P. Geiko, A. I. Gusamov, and Y. M. Andreev, "Optical properties and phase-matched conditions in nonlinear  $\text{AgGa}_x\text{In}_{1-x}\text{Se}_2$  crystals," *Atmospheric and Oceanic Optics*, vol. 2, pp. 606–610, 1999.
- [14] A. M. Prokhorova, *Handbook on Lasers*, Moscow, Russia, 1978.




Journal of  
Nanotechnology




International Journal of  
Corrosion




International Journal of  
Polymer Science

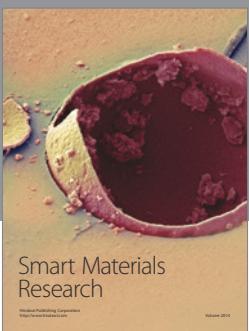


Smart Materials  
Research



Journal of  
Composites




BioMed  
Research International



Hindawi


Submit your manuscripts at  
<http://www.hindawi.com>




Journal of  
Metallurgy




Journal of  
Nanoparticles




Journal of  
Materials

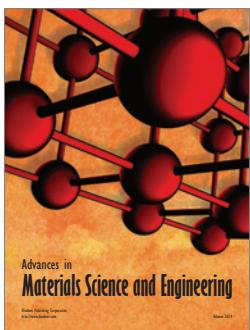


Advances in  
Materials Science and Engineering

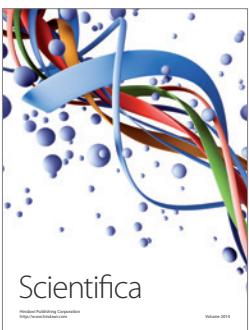

Scientifica

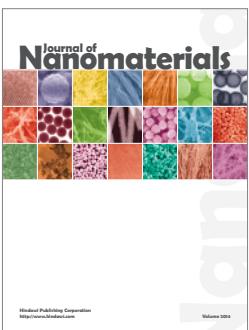

Journal of  
Nanomaterials

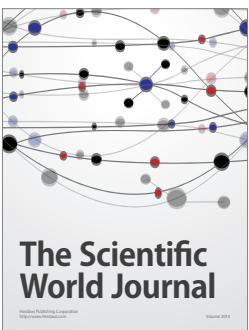

The Scientific  
World Journal



International Journal of  
Biomaterials



Journal of  
Nanoscience




Journal of  
Coatings



Journal of  
Crystallography



Journal of  
Ceramics

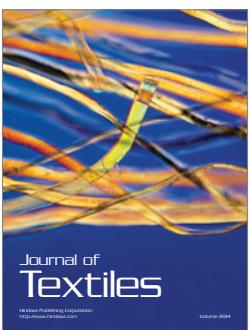

Journal of  
Textiles